



Version: 22 August 2017

# PLATUNA<sup>®</sup>- ALLOY 1

## PLATINUM RUTHENIUM ELECTROLYTE



### Extraordinarily Abrasion-Resistant Coatings – Saving Platinum

PLATUNA<sup>®</sup>-Alloy 1 is used for depositing smooth, ultra-bright and extraordinarily abrasion-resistant platinum-ruthenium alloy coatings. The acidic electrolyte is used for decorative applications and guarantees light, white layers - crack-free up to 1  $\mu\text{m}$ .

PLATUNA<sup>®</sup>-Alloy 1 works across a wide operating range and reaches an excellent covering speed. It is used for rack operation.



### Advantages

- Acidic platinum alloy electrolyte - saves expensive platinum
- Light, white and ultra-bright coatings
- For decorative applications
- Extraordinarily abrasion-resistant
- Wide operating range
- Up to 1  $\mu\text{m}$  layer thickness (crack-free)
- The coatings are RoHS compliant
- Suitable for racks

### Applications

- Jewellery
- Writing implements
- Watches
- Spectacle frames
- Accessories

# PLATUNA®-ALLOY 1

## PLATINUM RUTHENIUM ELECTROLYTE




### TECHNICAL SPECIFICATIONS

Electrolyte characteristics	
Electrolyte type	Strongly acidic
Metal content	1.0 (0.8 - 1.2) g/l Pt 1.0 (0.8 - 1.2) g/l Ru
pH value	< 1
Operating temperature	35 (30 - 40) °C
Current density range	2.0 (0.5 - 5.0) A/dm <sup>2</sup>
Plating speed	Approx. 0.08 µm/ min at 2.0 A/dm <sup>2</sup>
Anode material	MMO (type PLATINODE® 187 S0)

Coating characteristics	
Coating	Platinum-ruthenium
Alloy composition	75 weight % Pt 25 weight % Ru
Colour of deposit	White
Brightness	Bright
Hardness of deposit HV 0.015 (Vickers) approx. values	Not measurable, Approx. 500 HV
Max. coating thickness	1.0 µm
Density of the coating	Approx. 19.16 g/cm <sup>3</sup>

### Bosch-Weinmann Wear Test

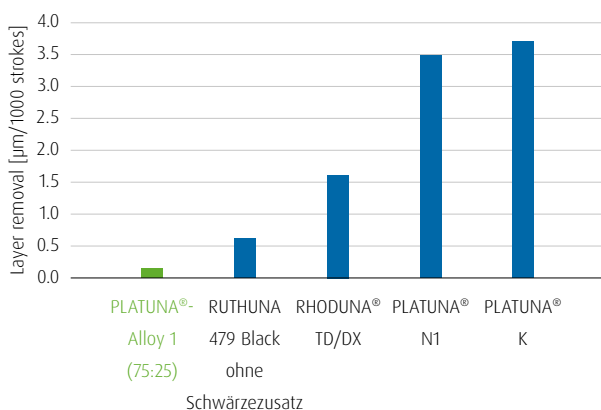

Umicore Galvanotechnik GmbH  
Klarenbergstrasse 53-79  
73525 Schwaebisch Gmuend (Germany)

Technical Support: Phone +49 7171 607-305  
Sales Department: Phone +49 7171 607-204

[www.ep.UMICORE.com](http://www.ep.UMICORE.com)

  
**umicore**  
Electroplating

The information and statements contained herein are based on our experience in the fields of research and applied technology and are believed to be accurate at the time of publication, but - unless agreed in writing - we make no warranty with respect thereto, including but not limited to any results to be obtained. This product information sheet in the English language prevails any translation.